




# Basic Quality Statistical Summary Report

**Plant** 1130-Green Bay Mine (FDOT Pit #16-608)  
**Product** 1001-FDOT Concrete Silica Sand Code F01  
**Specification** FLDOT Silica Sand  
**Period** 10/11/2024 - 10/18/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	8	100	0.0	95-100	95-100
#8 (2.36mm)	8	100	0.0	85-100	85-100
#16 (1.18mm)	8	94	0.5	67-96	65-97
#30 (.6mm)	8	58	2.4	27-68	25-70
#50 (.3mm)	8	25	4.4	7-33	5-35
#100 (.15mm)	8	1	0.5	0-6	0-7
#200 (75µm)	8	0	0.0	0-4	0-4
Pan	8	0	0.0		
FM	8	2.21	0.051	2.3	2.1-2.5
Grad Loss	8	0.028	0.0424		
Total Moisture	8	3.1	0.28		
D10 (ES)	8	0.1962	0.01489		
D50	8	0.50	0.024		
D60	8	0.62	0.025		
Cc	8	0.90	0.063		
Cu	8	3.16	0.237		

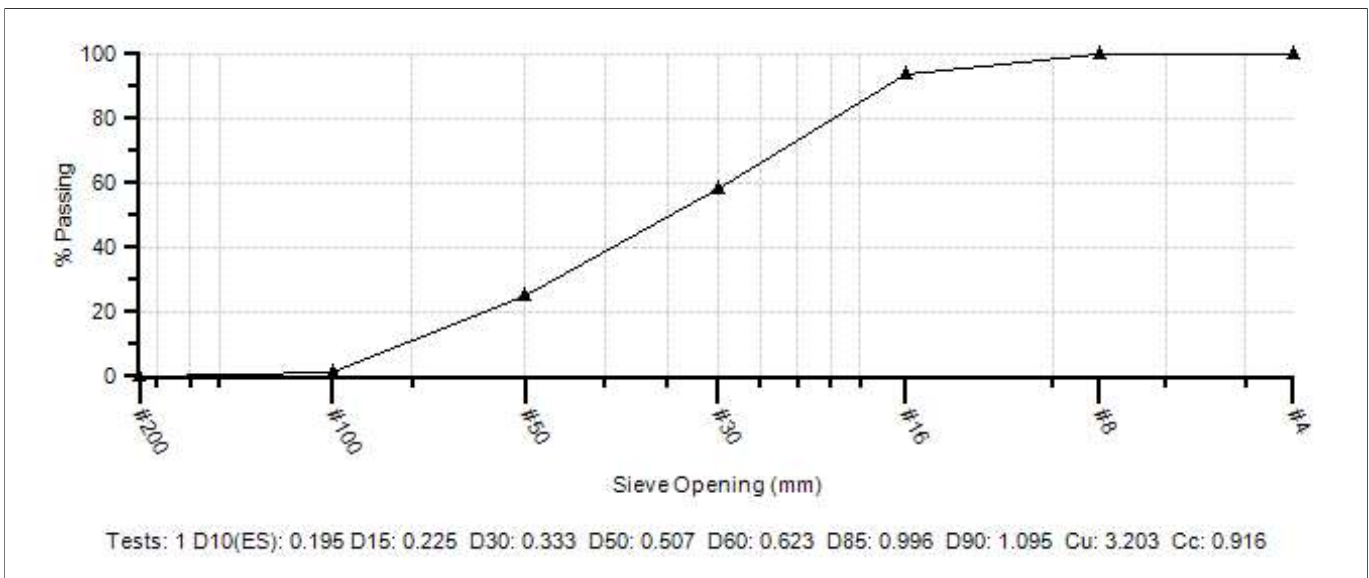

**Query**

Query Selections

Date Created 10/18/2024

Date Range 10/11/2024 - 10/18/2024

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping