




# Basic Quality Statistical Summary Report

**Plant** 1070-Independent South Mine (FDOT Pit#11-298)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 11/13/2024 - 11/20/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	6	99.9	0.12		95-100
#8 (2.36mm)	6	98.7	0.59		85-100
#16 (1.18mm)	6	91.2	2.41	67-98	65-99
#30 (.6mm)	6	68.7	5.76	27-79	25-80
#50 (.3mm)	6	35.4	10.01	7-38	5-40
#100 (.15mm)	6	3.7	1.81	0-6	0-7
#200 (75µm)	6	0.1	0.08		0-4
Pan	6	0.0	0.00		
FM	6	2.024	0.1778	1.87-2.18\2	1.85-2.2
Total Moisture	5	4.451	0.8019		
D10 (ES)	6	0.18	0.015		
D50	6	0.41	0.067		
D60	6	0.50	0.072		
Cc	6	0.86	0.113		
Cu	6	2.84	0.288		

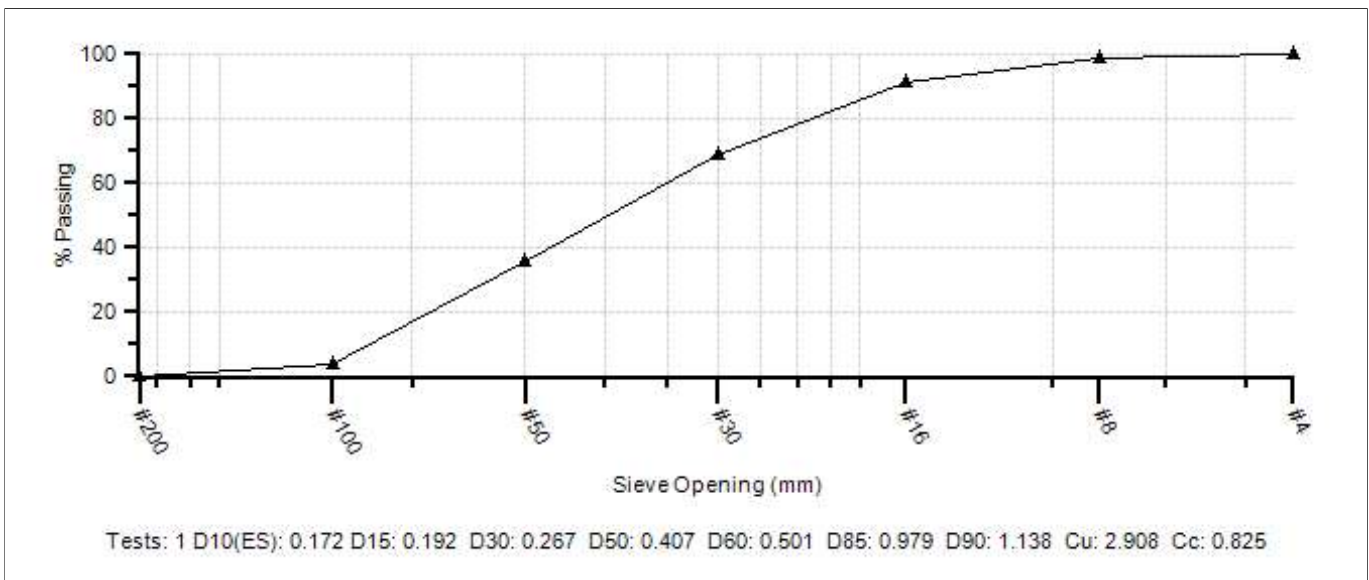

**Query**

Query Selections  
Date Created 11/20/2024  
Date Range 11/13/2024 - 11/20/2024  
Plant Independent South Mine (FDOT Pit#11-298)  
Sample Type Shipping