




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 11/13/2024 - 11/20/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	9	100	0.0	95-100	95-100
#8 (2.36mm)	9	100	0.0	85-100	85-100
#16 (1.18mm)	9	95	0.6	67-96	65-97
#30 (.6mm)	9	62	3.2	27-68	25-70
#50 (.3mm)	9	21	5.0	7-33	5-35
#100 (.15mm)	9	1	1.0	0-6	0-7
#200 (75µm)	9	0	0.0	0-4	0-4
Pan	9	0	0.0		
FM	9	2.21	0.050	2.3	2.1-2.5
-#200 (75um)	1	0.12			
Grad Loss	9	0.025	0.0381		
Wash Loss (#200/75um)	1	0.12			
Total Moisture	8	3.6	0.80		
Color	1	3			1-5
D10 (ES)	9	0.2100	0.02093		
D50	9	0.49	0.021		
D60	9	0.59	0.030		
Cc	9	0.98	0.065		
Cu	9	2.82	0.354		

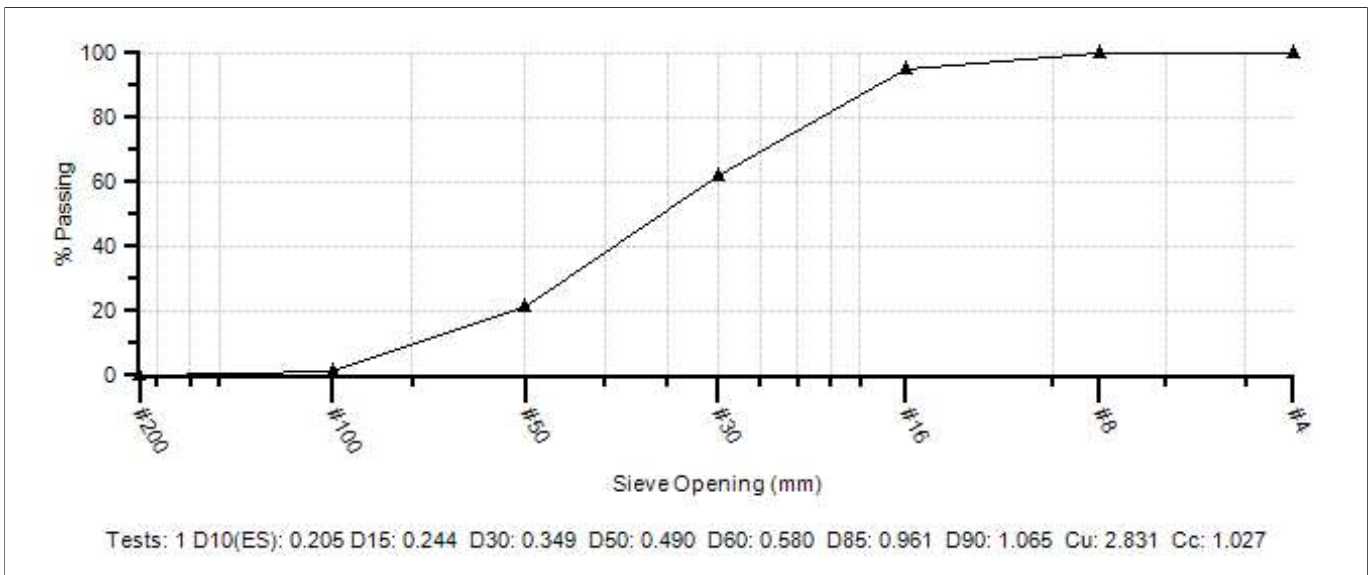

Query

Query Selections

Date Created 11/20/2024

Date Range 11/13/2024 - 11/20/2024

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping