




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 12/09/2024 - 12/16/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	15	100.0	0.00	95-100	
#8 (2.36mm)	15	99.9	0.07	85-100	
#16 (1.18mm)	15	96.4	1.40	65-97	
#30 (.6mm)	15	72.0	5.94	25-75	
#50 (.3mm)	15	37.2	4.42	5-40	
#100 (.15mm)	15	3.1	1.03	0-7	
#200 (75µm)	15	0.0	0.06		
Pan	15	0.0	0.00		
FM	15	1.91	0.118	1.82-2.18\2	1.8-2.2
-#200 (75um)	1	0.06			
Grad Loss	15	0.028	0.0495		
Wash Loss (#200/75um)	1	0.00			
Total Moisture	15	3.7	0.63	1-5	1-5
D10 (ES)	15	0.1731	0.00543		
D50	15	0.39	0.039		
D60	15	0.48	0.055		
Cc	15	0.83	0.048		
Cu	15	2.76	0.245		

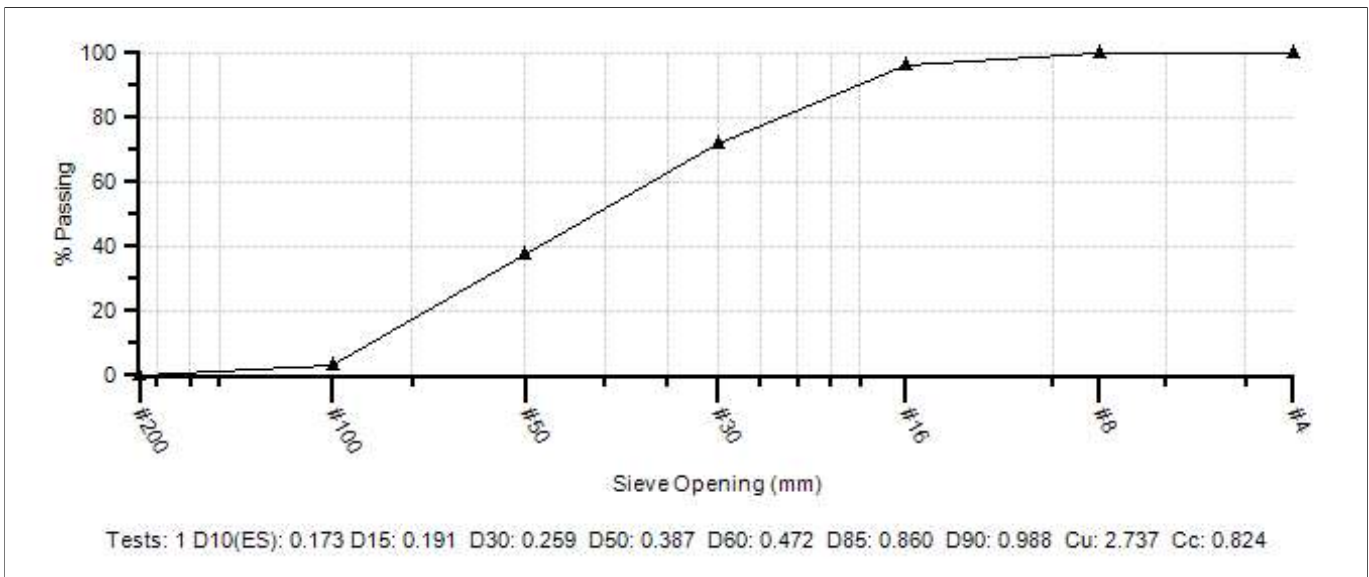

Query

Query Selections

Date Created 12/16/2024

Date Range 12/09/2024 - 12/16/2024

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping