




Basic Quality Statistical Summary Report

Plant 1030-Haines City Mine (FDOT Pit #16-024)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 12/09/2024 - 12/16/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	7	100.0	0.00	95-100	95-100
#8 (2.36mm)	7	99.9	0.05	85-100	85-100
#16 (1.18mm)	7	96.8	0.77	65-98	65-100
#30 (.6mm)	7	75.1	3.37	25-75	≥25
#50 (.3mm)	7	41.1	3.23	5-44	5-45
#100 (.15mm)	7	6.4	1.59	0-10	0-10
#200 (75µm)	7	0.1	0.05	0-4	0-4
Pan	7	0.0	0.00		
FM	7	1.81	0.082	1.8-2.2\2	
Total Moisture	7	3.5	0.44	0-5	0-6
D10 (ES)	7	0.16	0.009		
D50	7	0.36	0.025		
D60	7	0.44	0.027		
Cc	7	0.82	0.021		
Cu	7	2.74	0.130		

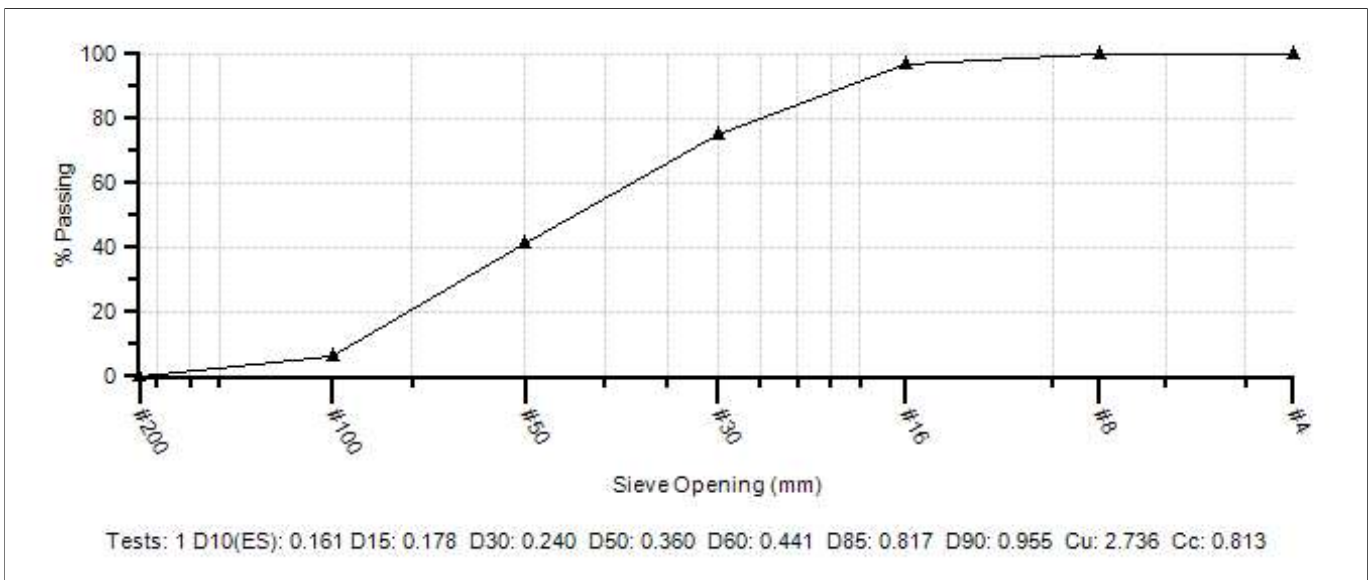

Query

Query Selections

Date Created 12/16/2024

Date Range 12/09/2024 - 12/16/2024

Plant Haines City Mine (FDOT Pit #16-024)

Sample Type Shipping