




Basic Quality Statistical Summary Report

Plant 2010-Ortona Sand Company (FDOT Pit # 05-045)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 12/09/2024 - 12/16/2024

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	6	100.0	0.00	95-100	
#8 (2.36mm)	6	99.9	0.05	85-100	
#16 (1.18mm)	6	96.6	0.21	65-99	
#30 (.6mm)	6	56.2	1.81	25-70	
#50 (.3mm)	6	18.4	2.90	5-35	
#100 (.15mm)	6	1.5	0.65	0-7	
#200 (75µm)	6	0.0	0.00		
Pan	6	0.0	0.00		
FM	6	2.27	0.047		
Total Moisture	6	3.7	0.12		
D10 (ES)	6	0.21	0.015		
D50	6	0.54	0.021		
D60	6	0.64	0.017		
D15/D85	6	0.27	0.023		
Cc	6	1.00	0.022		
Cu	6	2.99	0.139		

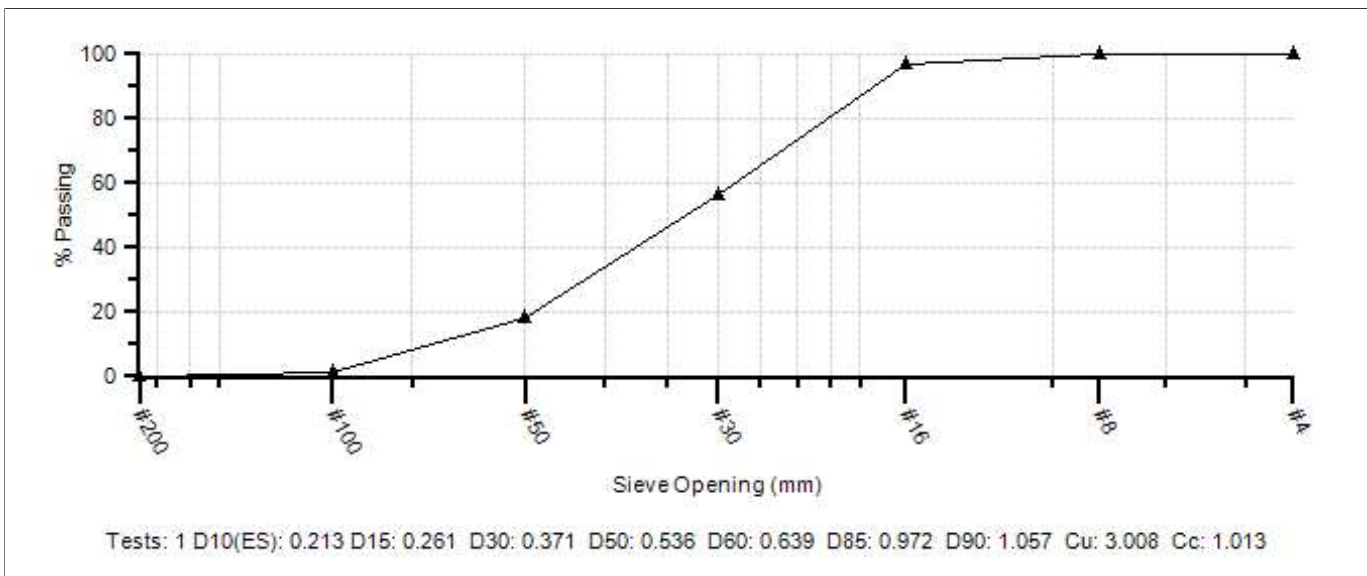

Query

Query Selections
Date Created 12/16/2024
Date Range 12/09/2024 - 12/16/2024
Plant Ortona Sand Company (FDOT Pit # 05-045)
Sample Type Shipping