




# Basic Quality Statistical Summary Report

**Plant** 1030-Haines City Mine (FDOT Pit #16-024)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 12/23/2024 - 01/03/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	8	100.0	0.00	95-100	95-100
#8 (2.36mm)	8	99.9	0.05	85-100	85-100
#16 (1.18mm)	8	96.6	0.60	65-98	65-100
#30 (.6mm)	8	72.9	3.10	25-75	≥25
#50 (.3mm)	8	39.2	3.52	5-44	5-45
#100 (.15mm)	8	6.5	0.94	0-10	0-10
#200 (75µm)	8	0.1	0.07	0-4	0-4
Pan	8	0.0	0.00		
FM	8	1.85	0.056	1.8-2.2\2	
Total Moisture	8	3.8	0.41	0-5	0-6
D10 (ES)	8	0.16	0.005		
D50	8	0.38	0.024		
D60	8	0.46	0.029		
Cc	8	0.83	0.048		
Cu	8	2.85	0.163		

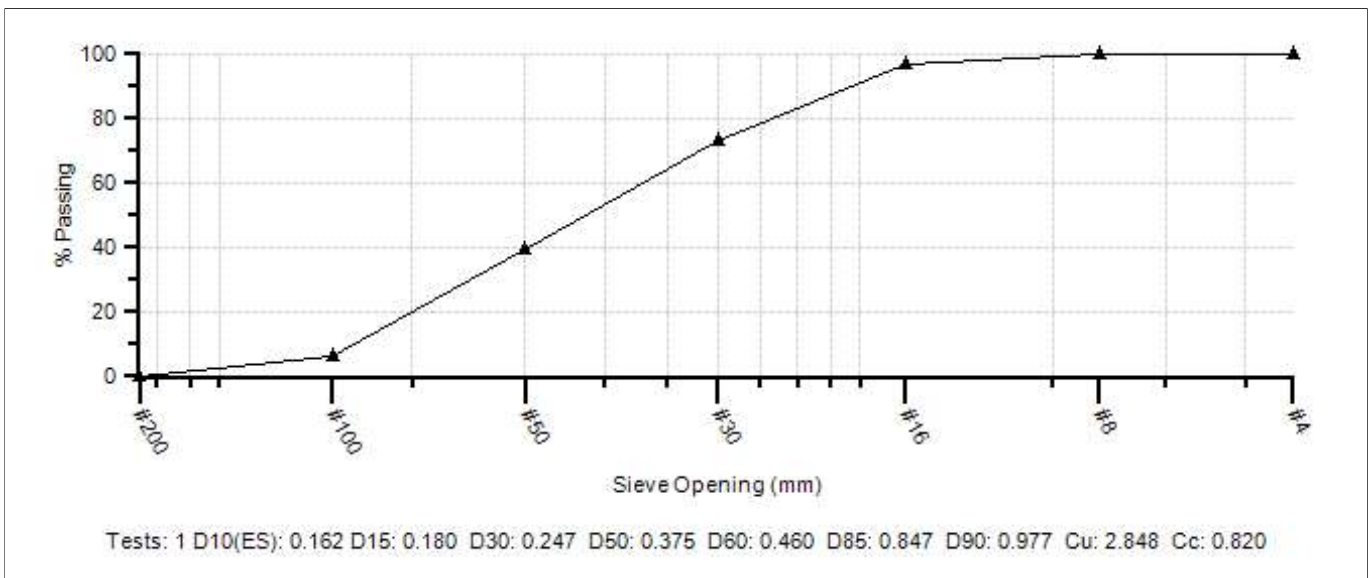

**Query**

Query Selections

Date Created 01/03/2025

Date Range 12/23/2024 - 01/03/2025

Plant Haines City Mine (FDOT Pit #16-024)

Sample Type Shipping