




# Basic Quality Statistical Summary Report

**Plant** 1050-Independent North Mine (FDOT Pit #11-490)  
**Product** 1009-Concrete Sand  
**Specification** Concrete Sand  
**Period** 02/14/2025 - 02/21/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	10	100.0	0.00		95-100
#8 (2.36mm)	10	99.7	0.05		85-100
#16 (1.18mm)	10	94.7	0.92	67-98	65-99
#30 (.6mm)	10	69.4	2.65	27-79	25-80
#50 (.3mm)	10	27.0	2.69	7-38	5-40
#100 (.15mm)	10	1.4	0.31	0-6	0-7
#200 (75µm)	10	0.1	0.13		0-4
Pan	10	0.0	0.00		
FM	10	2.08	0.062	1.87-2.18\2	1.85-2.2
Total Moisture	10	4.0	0.70		
D10 (ES)	10	0.1898	0.00581		
D50	10	0.44	0.019		
D60	10	0.52	0.023		
Cc	10	1.01	0.022		
Cu	10	2.71	0.050		

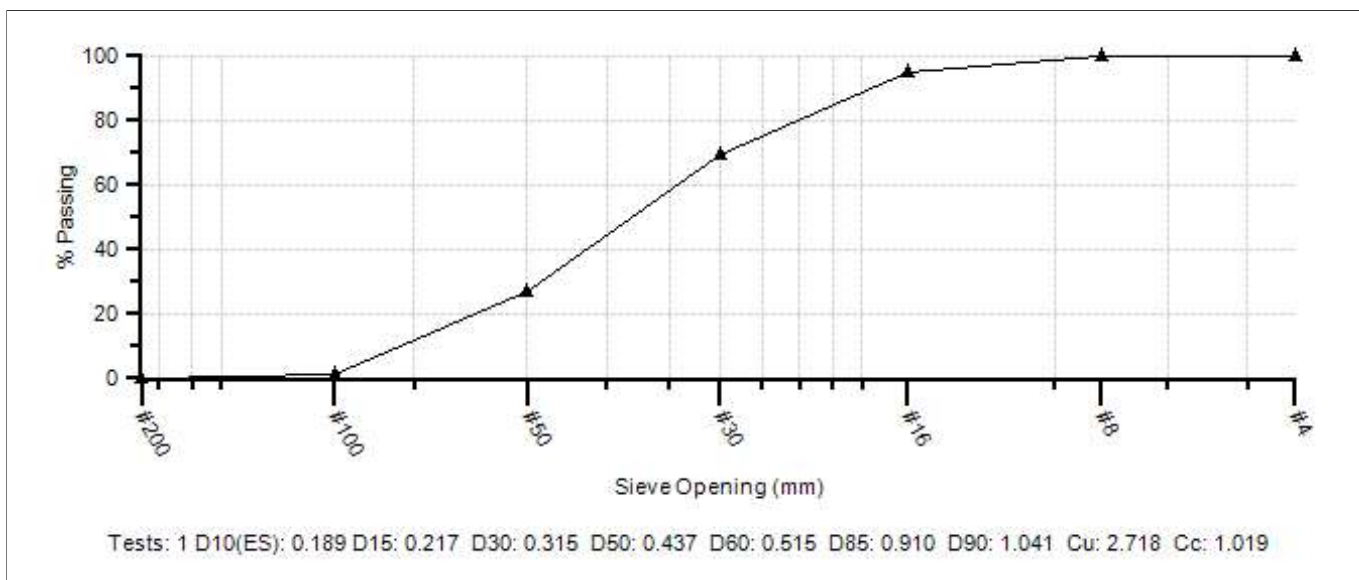

**Query**

Query Selections  
Date Created 02/21/2025  
Date Range 02/14/2025 - 02/21/2025  
Plant Independent North Mine (FDOT Pit #11-490)  
Sample Type Shipping