




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 02/14/2025 - 02/21/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	12	100	0.0	95-100	95-100
#8 (2.36mm)	12	100	0.0	85-100	85-100
#16 (1.18mm)	12	95	0.9	67-96	65-97
#30 (.6mm)	12	61	2.8	27-68	25-70
#50 (.3mm)	12	24	3.2	7-33	5-35
#100 (.15mm)	12	1	0.5	0-6	0-7
#200 (75µm)	12	0	0.0	0-4	0-4
Pan	12	0	0.0		
FM	12	2.20	0.047	2.3	2.1-2.5
-#200 (75um)	1	0.02			
Grad Loss	12	0.017	0.0350		
Wash Loss (#200/75um)	1	0.02			
Total Moisture	11	3.2	0.35		
Color	1	3			1-5
D10 (ES)	12	0.1995	0.00891		
D50	12	0.49	0.020		
D60	12	0.59	0.031		
Cc	12	0.96	0.057		
Cu	12	2.95	0.190		

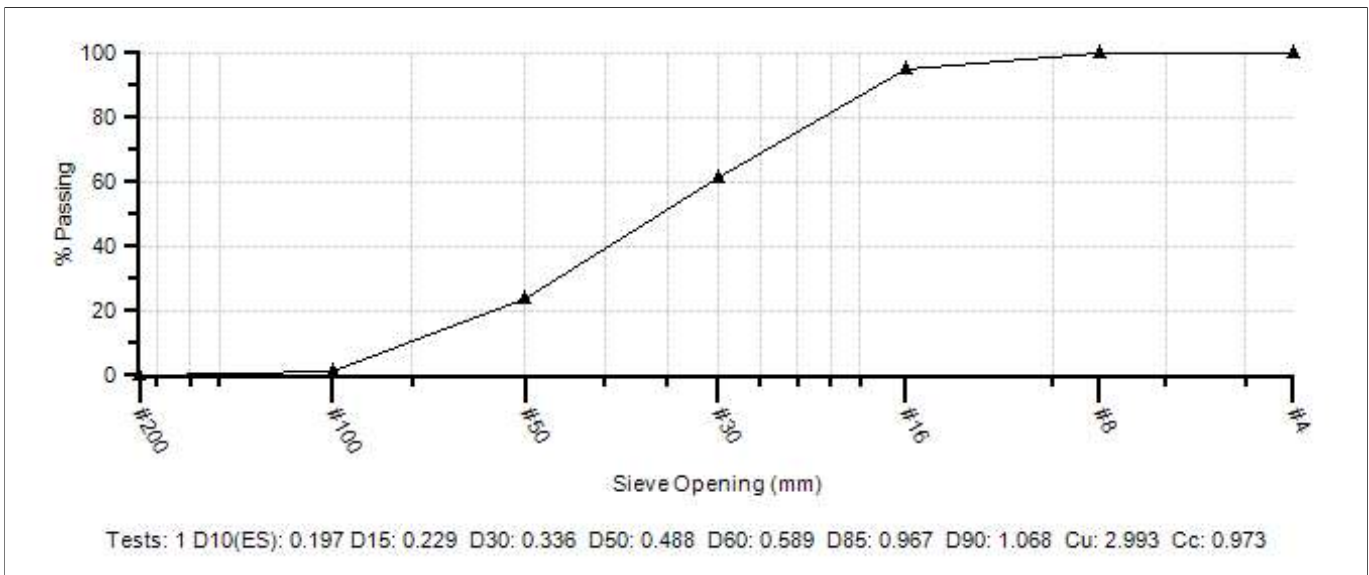

Query

Query Selections

Date Created 02/21/2025

Date Range 02/14/2025 - 02/21/2025

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping