




Basic Quality Statistical Summary Report

Plant 2010-Ortona Sand Company (FDOT Pit # 05-045)
Product 1008-Mason Sand
Specification Mason Sand
Period 02/14/2025 - 02/21/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	6	100	0.0	100-100	
#8 (2.36mm)	6	100	0.0	100-100	
#16 (1.18mm)	6	98	0.0	97-100	
#30 (.6mm)	6	78	5.4	80-100	
#50 (.3mm)	6	44	4.7	43-85	
#100 (.15mm)	6	4	2.0	0-25	
#200 (75µm)	6	0.1	0.00		
Pan	6	0.0	0.00		
FM	6	1.76	0.058		
Grad Loss	6	0.000	0.0000		
Total Moisture	6	4.4	0.23	0-5	0-6
D10 (ES)	6	0.17	0.005		
D50	6	0.34	0.029		
D60	6	0.42	0.022		
D15/D85	6	0.25	0.046		
Cu	6	2.48	0.106		

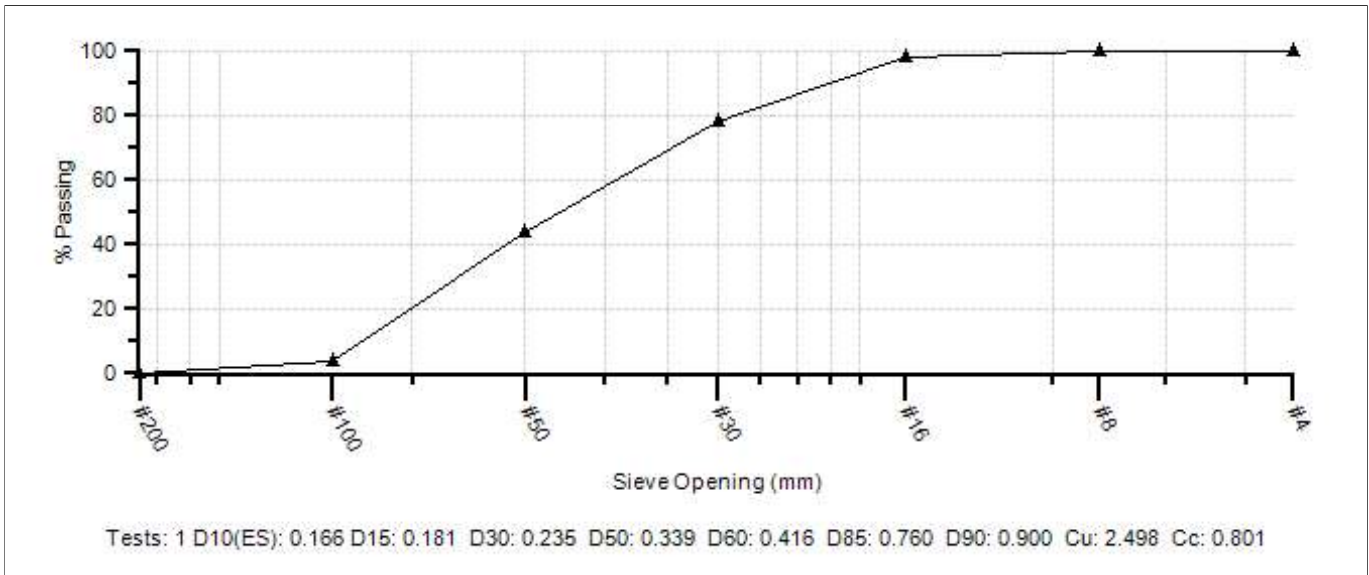

Query

Query Selections
Date Created 02/21/2025
Date Range 02/14/2025 - 02/21/2025
Plant Ortona Sand Company (FDOT Pit # 05-045)
Sample Type Shipping