




Basic Quality Statistical Summary Report

Plant 1130-Green Bay Mine (FDOT Pit #16-608)
Product 1001-FDOT Concrete Silica Sand Code F01
Specification FLDOT Silica Sand
Period 03/12/2025 - 03/19/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	12	100	0.0	95-100	95-100
#8 (2.36mm)	12	100	0.0	85-100	85-100
#16 (1.18mm)	12	95	0.8	67-96	65-97
#30 (.6mm)	12	62	1.7	27-68	25-70
#50 (.3mm)	12	20	6.0	7-33	5-35
#100 (.15mm)	12	0	0.5	0-6	0-7
#200 (75µm)	12	0	0.0	0-4	0-4
Pan	12	0	0.0		
FM	12	2.23	0.067	2.3	2.1-2.5
-#200 (75um)	1	0.15			
Grad Loss	12	0.017	0.0325		
Wash Loss (#200/75um)	1	0.15			
Total Moisture	12	3.3	0.36		
Color	1	3			1-5
D10 (ES)	12	0.2186	0.02727		
D50	12	0.49	0.019		
D60	12	0.58	0.020		
Cc	12	0.98	0.069		
Cu	12	2.69	0.295		

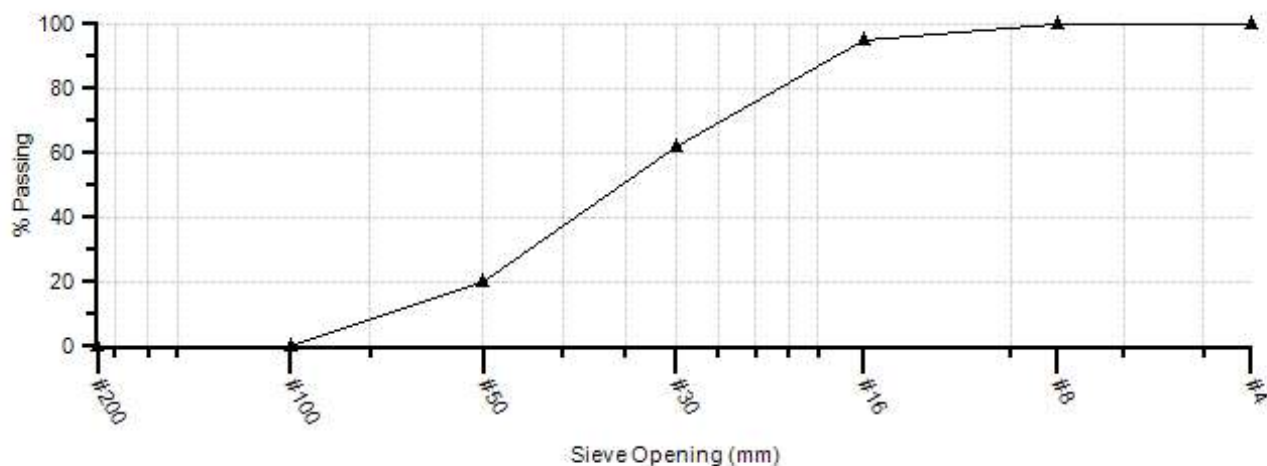

Query

Query Selections

Date Created 03/19/2025

Date Range 03/12/2025 - 03/19/2025

Plant Green Bay Mine (FDOT Pit #16-608)

Sample Type Shipping