




Basic Quality Statistical Summary Report

Plant 1030-Haines City Mine (FDOT Pit #16-024)
Product 1009-Concrete Sand
Specification Concrete Sand
Period 03/12/2025 - 03/19/2025

Sieve/Test	Tests	Average	St Dev	Target	Specification
#4 (4.75mm)	6	100.0	0.00	95-100	95-100
#8 (2.36mm)	6	99.8	0.06	85-100	85-100
#16 (1.18mm)	6	95.1	0.66	65-98	65-100
#30 (.6mm)	6	67.9	3.31	25-75	≥25
#50 (.3mm)	6	39.2	3.47	5-44	5-45
#100 (.15mm)	6	7.9	0.93	0-10	0-10
#200 (75µm)	6	0.1	0.05	0-4	0-4
Pan	6	0.0	0.00		
FM	6	1.90	0.074	1.8-2.2\2	
Total Moisture	6	3.6	1.08	0-5	0-6
D10 (ES)	6	0.16	0.004		
D50	6	0.39	0.032		
D60	6	0.50	0.039		
Cc	6	0.78	0.031		
Cu	6	3.16	0.236		

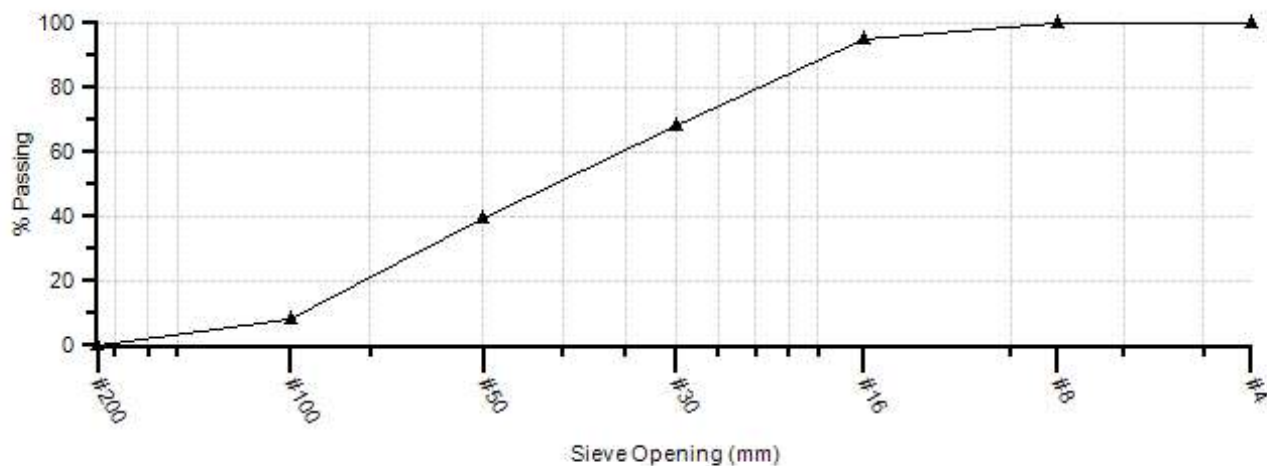

Query

Query Selections

Date Created 03/19/2025

Date Range 03/12/2025 - 03/19/2025

Plant Haines City Mine (FDOT Pit #16-024)

Sample Type Shipping